

Crystal structure of $K_3EuSi_2O_7$

Sabina Kovač, Predrag Dabić, Aleksandar Kremenović



Дигитални репозиторијум Рударско-геолошког факултета Универзитета у Београду

[ДР РГФ]

Crystal structure of $K_3EuSi_2O_7$ | Sabina Kovač, Predrag Dabić, Aleksandar Kremenović | Journal of the Serbian Chemical Society | 2021 | |

10.2298/JSC210218026K

<http://dr.rgf.bg.ac.rs/s/repo/item/0005033>

Дигитални репозиторијум Рударско-геолошког факултета Универзитета у Београду омогућава приступ издањима Факултета и радовима запослених доступним у слободном приступу. - Претрага репозиторијума доступна је на www.dr.rgf.bg.ac.rs

The Digital repository of The University of Belgrade Faculty of Mining and Geology archives faculty publications available in open access, as well as the employees' publications. - The Repository is available at: www.dr.rgf.bg.ac.rs



ACCEPTED MANUSCRIPT

This is an early electronic version of an as-received manuscript that has been accepted for publication in the Journal of the Serbian Chemical Society but has not yet been subjected to the editing process and publishing procedure applied by the JSCS Editorial Office.

Please cite this article as S. Z. Kovač, P. Z. Dabić, A. S. Kremenović, *J. Serb. Chem. Soc.* (2021) <https://doi.org/10.2298/JSC210218026K>

This “raw” version of the manuscript is being pvided to the authors and readers for their technical service. It must be stressed that the manuscript still has to be subjected to copyediting, typesetting, English grammar and syntax corrections, professional editing and authors’ review of the galley proof before it is published in its final form. Please note that during these publishing processes, many errors may emerge which could affect the final content of the manuscript and all legal disclaimers applied according to the policies of the Journal.

Crystal structure of $K_3EuSi_2O_7$

SABINA Z. KOVAČ*, PREDRAG Z. DABIĆ and ALEKSANDAR S. KREMENOVIĆ

University of Belgrade, Faculty of Mining and Geology, Department of Mineralogy,
Crystallography, Petrology and Geochemistry, Laboratory of Crystallography, Đušina 7,
Belgrade 11000, Serbia

(Received 18 February; Revised 15 March 2021; Accepted 31 March 2021)

Abstract: As a part of the research of the flux technique for growing alkali rare-earth elements (REE) containing silicates, tripotassium europium disilicate, $K_3EuSi_2O_7$, has been synthesized and characterized by single-crystal X-ray diffraction. It crystallizes in the space group $P6_3/mcm$. In the crystal structure of the title compound, one part of the Eu cations are in a slightly distorted octahedral coordination and the other part are in an ideal trigonal prismatic coordination environment. The disilicate Si_2O_7 groups connect four EuO_6 octahedra and one EuO_6 trigonal prism. Three differently coordinated potassium cations are located between them. Silicates containing the larger rare earth elements usually crystallize in a structure that contains the rare-earth cation in both a slightly distorted octahedral and an ideal trigonal prismatic coordination environment.

Keywords: alkali rare-earth silicates; crystal structure; flux synthesis; single-crystal X-ray diffraction.

INTRODUCTION

Silicates containing rare-earth elements (REE silicates) are the subject of intense research in recent decades. Many studies were performed on REE silicates because of a wide range of optical and magnetic properties combined with high thermal stability.¹⁻⁹ All this makes them very interesting and promising materials for different applications. REE silicates also exhibit a broad structural diversity.¹⁰ A highly adaptive framework can incorporate almost all REEs and this opens the possibility of synthesizing numerous structures and structural series of REE-containing silicates. Small but systematic variations in cation radii among the lanthanides allow extensive cation substitutions.

Several ternary potassium-REE silicates with the stoichiometric composition $K_3REESi_2O_7$ which crystallize in the space groups $P6_3/mcm$ and $P6_3/mmc$ have been described so far: $K_3EuSi_2O_7$,¹¹ $K_3NdSi_2O_7$,¹² $K_3REESi_2O_7$ ($REE = Gd-Lu$),¹³

*Corresponding author: sabina.kovac@rgf.bg.ac.rs
<https://doi.org/10.2298/JSC210218026K>

$\text{K}_3\text{ScSi}_2\text{O}_7$,¹⁴ $\text{K}_3\text{YSi}_2\text{O}_7$ (2 polymorphs),⁶ $\text{K}_3\text{SmSi}_2\text{O}_7$,⁷ $\text{K}_3\text{ErSi}_2\text{O}_7$ (2 polymorphs).¹⁵

During our investigations focused on the synthesis of new potassium-REE silicates, single crystals of $\text{K}_3\text{EuSi}_2\text{O}_7$ were obtained. $\text{K}_3\text{EuSi}_2\text{O}_7$ crystallizes in the hexagonal space group $P6_3/mcm$ (No. 193) and is isostructural with $\text{K}_3\text{NdSi}_2\text{O}_7$,¹² $\text{K}_3\text{REESi}_2\text{O}_7$ (REE = Gd–Yb),¹³ $\text{K}_3\text{YSi}_2\text{O}_7$,⁶ $\text{K}_3\text{SmSi}_2\text{O}_7$,⁷ $\text{K}_3\text{ErSi}_2\text{O}_7$.¹⁵ The reported compound is already known in the literature. Bondar and co-authors¹¹ stated the existence of this phase, however, they reported only unit cell parameters ($a = 9.98(1)$, $c = 14.44(2)$ Å), space group ($P6_3/mcm$), chemical composition and described the morphology of crystals. Myers¹⁶ outlined the successful synthesis of $\text{K}_3\text{REESi}_2\text{O}_7$ (REE = Eu, Y, Sc), but without any peer-reviewed data for $\text{K}_3\text{EuSi}_2\text{O}_7$. Thus, the crystal structure of this compound, $\text{K}_3\text{EuSi}_2\text{O}_7$, has not been described in the literature so far.

EXPERIMENTAL

Materials and measurements

All the materials were of analytical reagent grade and used as received without further purification. The crystal structure of $\text{K}_3\text{EuSi}_2\text{O}_7$ was analyzed by the single-crystal X-ray diffraction method. Diffraction experiments were conducted on a Gemini S (Oxford Diffraction) four-circle diffractometer equipped with a Mo-anode sealed tube and a Sapphire3 CCD detector. Diffraction data were processed with the CrysAlis^{Pro}.¹⁷ The synthesized products were tested using X-ray powder diffraction (XRPD). A small amount of material was finely ground and tested on a Philips PW1710 X-ray powder diffractometer at room temperature using Bragg-Brentano geometry and Cu K α radiation. The diffractometer was operated at 40 kV and 30 mA, while the scan range was from 3 to 60° 2 θ , with a step size of 0.02° and time per step of 1.25 s. PDXL 2 software¹⁸ was used for the powder diffraction data analysis. Scanning electron microscopy (SEM) was used for the morphological characterization. The analyses were carried out on a single crystal using a JEOL JSM-6610LV instrument equipped with an Oxford INCA Energy 350 EDS detector.

Synthesis and crystallization

The following chemicals were used in the high-temperature flux synthesis experiment: Eu_2O_3 (Sigma-Aldrich, 99.99 %), SiO_2 (Merck, p.a.) and KF (Centrohem, 99 %). A total of 0.055 g of a mixture of Eu_2O_3 and SiO_2 in a molar ratio of 1:4 was added to 1 g of KF. The resulting mixture was homogenized in an agate mortar, transferred to a platinum crucible covered with a platinum lid and placed in a resistance-heated furnace. The mixture was heated to 1173 K at a rate of 200 K/h and kept for 10 h at that temperature. The temperature was lowered to 973 K at a rate of 2 K/h and then the furnace was switched off. After cooling to room temperature, the resulting material was manually removed from the crucible, washed with distilled water and dried in air. Bow-tie aggregate colorless crystals up to 300 μm size embedded in a polycrystalline matrix were observed.

X-ray structure determination

Selected elongated prismatic colorless single crystal was fixed on glass fiber using nail polish as glue and room-temperature X-ray diffraction data were collected. Relevant information on the crystal data, data collection and structure refinement are compiled in Table I.

An analytical absorption correction based on indexed crystal faces using the procedure of Clark & Reid¹⁹ in combination with an empirical absorption correction using spherical harmonics (implemented in SCALE3 ABSPACK scaling algorithm) were applied during the data reduction. The structure of $K_3EuSi_2O_7$ crystallizes in space group $P6_3/mcm$. Since it is isostructural with $K_3ErSi_2O_7$,¹⁵ atomic coordinates of this structural analogue were used as a starting model for structure refinement. When Er^{3+} was replaced with Eu^{3+} the model converged rapidly, and the crystal structure was refined to $R = 3.5\%$. The structure was refined on F^2 by full-matrix least-squares techniques using the programs *SHELXL*.²⁰ Selected bond lengths and angles are presented in Table II. All figures of the crystal structures were prepared using the program *VESTA*.²¹

TABLE I. Experimental details.

Crystal data		Data collection	
Chemical formula	$K_3EuSi_2O_7$	Diffractometer	Gemini S (Oxford Diffraction)
M_r	437.44	Absorption correction	Analytical + Empirical
Crystal system	Hexagonal	Measured reflections	10007
Space group	$P6_3/mcm$	Independent reflections	528
Temperature, K	298	Observed [$I > 2\sigma(I)$] reflections	392
$a / \text{\AA}$	9.9512 (3)	R_{int}	0.077
$c / \text{\AA}$	14.4480 (4)	$(\sin \theta/\lambda)_{max} / \text{\AA}^{-1}$	0.641
$\alpha / ^\circ$	90	Refinement	
$\gamma / ^\circ$	120	$R[F^2 > 2\sigma(F^2)]$	0.035
$V / \text{\AA}^3$	1239.05 (8)	$wR(F^2)$	0.069
Z	6	S	1.13
Radiation type	Mo $K\alpha$	No. of reflections	528
μ / mm^{-1}	9.39	No. of parameters	40
Crystal size, mm	0.27×0.04×0.04	$\Delta\rho_{max}; \Delta\rho_{min} / e \text{\AA}^{-3}$	1.01; - 0.69

Table II. Selected geometric parameters for $K_3EuSi_2O_7$. Symmetry codes are given in footnotes

Bond length, \AA		Bond length, \AA	
K1–O1	2.770 (5)	K3–O2 ^{xii}	2.754 (7)
K1–O1 ⁱ	2.770 (5)	K3–O2 ^{xiii}	2.754 (7)
K1–O2 ⁱ	2.962 (3)	K3–O2	2.754 (7)
K1–O2	2.962 (3)	Eu1–O1 ^{iv}	2.282 (4)
K1–O1 ⁱⁱ	3.006 (6)	Eu1–O1 ⁱ	2.282 (4)
K1–O1 ⁱⁱⁱ	3.006 (6)	Eu1–O1 ^{xiv}	2.282 (4)
K1–O1 ^{iv}	3.049 (5)	Eu1–O1 ⁱⁱⁱ	2.282 (4)
K1–O1 ^v	3.049 (5)	Eu1–O1 ^{viii}	2.282 (4)
K2–O1 ⁱ	2.923 (4)	Eu1–O1 ^{xv}	2.282 (4)
K2–O1 ^{vi}	2.923 (4)	Eu2–O2 ^{vii}	2.334 (7)
K2–O1 ^{vii}	2.923 (4)	Eu2–O2	2.334 (7)
K2–O1 ⁱⁱⁱ	2.923 (4)	Eu2–O2 ^{xi}	2.334 (7)
K2–O1 ^{viii}	2.923 (4)	Eu2–O2 ⁱ	2.334 (7)
K2–O1 ^{ix}	2.923 (4)	Eu2–O2 ^{xvi}	2.334 (7)
K2–O3 ^{viii}	3.029 (3)	Eu2–O2 ^{xvii}	2.334 (7)
K2–O3	3.029 (3)	Si1–O1 ⁱⁱⁱ	1.616 (5)
K2–O3 ⁱⁱⁱ	3.029 (3)	Si1–O1 ⁱⁱ	1.616 (5)

Bond length, Å		Bond length, Å	
K3–O2 ⁱ	2.754 (7)	Si1–O2 ^{xviii}	1.622 (7)
K3–O2 ^x	2.754 (7)	Si1–O3	1.661 (4)
K3–O2 ^{xi}	2.754 (7)		
Bond angle, °		Bond angle, °	
O1 ⁱⁱⁱ –Si1–O1 ⁱⁱ	111.0 (4)	O1 ⁱⁱ –Si1–O3	106.7 (2)
O1 ⁱⁱⁱ –Si1–O2 ^{xviii}	110.9 (2)	O2 ^{xviii} –Si1–O3	110.5 (4)
O1 ⁱⁱ –Si1–O2 ^{xviii}	110.9 (2)	Si1–O3–Si1 ^{xvii}	136.7 (6)
O1 ⁱⁱⁱ –Si1–O3	106.7 (2)		

ⁱ $x-y, -y, z$; ⁱⁱ $-y+1, x-y, z$; ⁱⁱⁱ $-x+1, -x+y, z$; ^{iv} $y, -x+y, -z$; ^v $x, x-y, -z$; ^{vi} $-x+1, -x+y, -z+1/2$; ^{vii} $x-y, -y, -z+1/2$; ^{viii} $y, x-1, z$; ^{ix} $y, x-1, -z+1/2$; ^x $-x+y, y, -z$; ^{xi} y, x, z ; ^{xii} $-y, -x, -z$; ^{xiii} $-x, -y, -z$; ^{xiv} $x-y, x-1, -z$; ^{xv} $-x+1, -y, -z$; ^{xvi} $y, x, -z+1/2$; ^{xvii} $x, y, -z+1/2$; ^{xviii} $y+1, x, z$

RESULTS AND DISCUSSION

Description of the crystal structure

As a result of an extensive study of the flux technique for growing new alkali rare-earth elements (REE) containing silicates, $K_3EuSi_2O_7$ has been synthesized and characterized by single-crystal X-ray diffraction. The compound crystallizes in the space group $P6_3/mcm$ and is isostructural with disilicates $K_3ErSi_2O_7$ ¹⁵ and $K_3YbSi_2O_7$.²² The crystal structure is comparable to the sorosilicate structure type reported earlier by Vidican and co-authors.¹³

The crystal structure of the title compound consists of Si_2O_7 groups and EuO_6 polyhedra which form a 3D framework with potassium ions in the holes (Fig. 1).

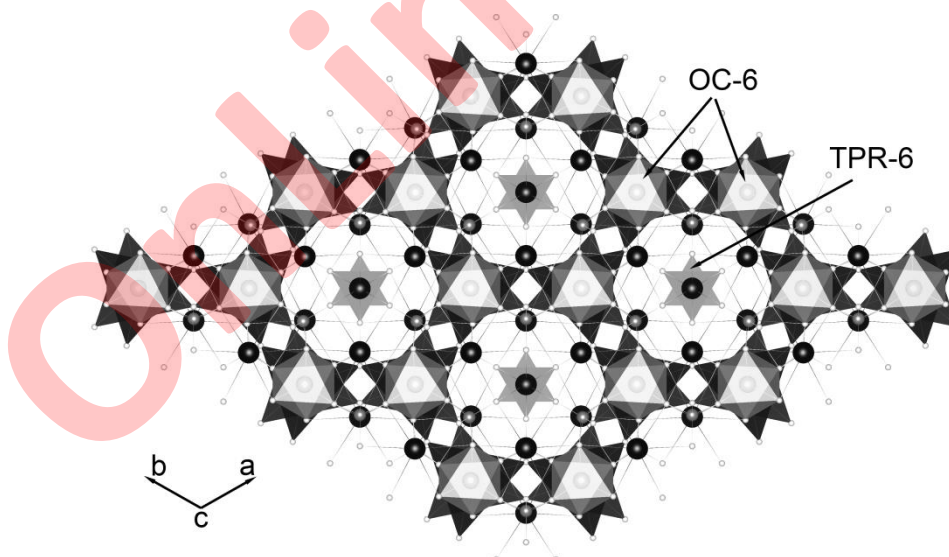


Fig.1. The framework in the crystal structure of $K_3EuSi_2O_7$ along [001]. Color code: K atoms and polyhedra are black, EuO_6 polyhedra are grey (octahedra: OC-6; trigonal prisms: TPR-6), Si atoms are dark grey and O atoms are white.

The disilicate groups Si_2O_7 connect four EuO_6 octahedra (OC-6), as well as one EuO_6 trigonal prism (TPR-6) (Fig. 2). Three differently coordinated potassium cations are located between them. The structure can also be described as regular alternation of two types of layers, which are parallel to the (001) plane: (I) octahedral layers and (II) sorosilicate layers, formed by a mixture of Si_2O_7 -groups and K_2O_{6+3} polyhedra (Fig. 3).

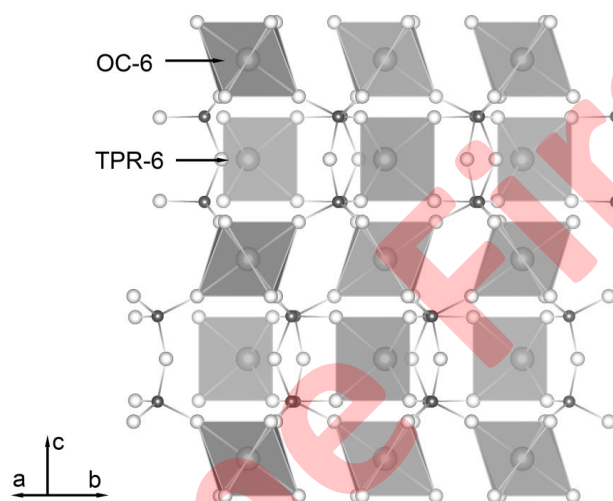


Fig. 2. The Si_2O_7 groups and EuO_6 polyhedra (octahedra: OC-6; trigonal prisms: TPR-6) in the crystal structure of $K_3EuSi_2O_7$ oriented approximately along [120] (c -axis is vertical) showing their connections. Potassium cations have been omitted for clarity. Color code: Eu atoms and polyhedra are grey, Si atoms are dark grey and O atoms are white.

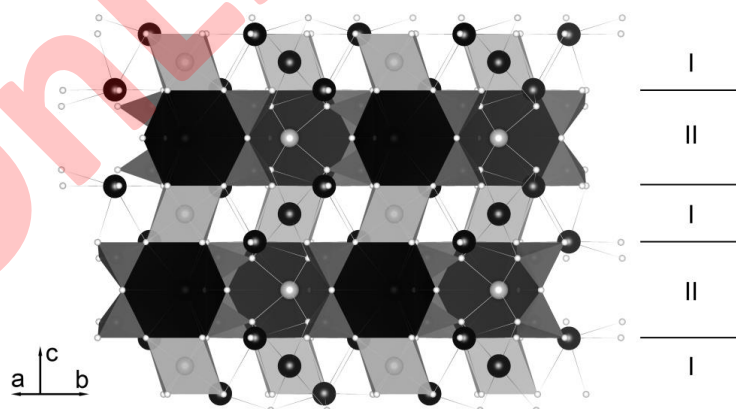


Fig. 3. Projection of structure along [120] showing two types of regularly alternating layers, which are parallel to the (001) plane: (I) octahedral layers and (II) sorosilicate layers. K atoms and polyhedra are black, Eu atoms and polyhedra are dark grey and SiO_4 polyhedra are dark grey and O atoms are white.

The structure is characterized by two crystallographically distinct six-coordinated sites occupied by Eu1 and Eu2: Eu1O₆ is an octahedron (OC-6) and Eu2O₆ is a trigonal prism (TPR-6). Two types of polyhedra around europium cations are distinguished by a small difference in the Eu–O distances: all Eu1–O distances are 2.282 (4) Å, while all Eu2–O bond lengths are 2.334 (7) Å. Each Eu1O₆ octahedron (OC-6) shares its six corners with six different Si₂O₇ groups, while each Er₂O₆ trigonal prism (TPR-6) also shares six corners, but with only three different Si₂O₇ groups.

Each Si₂O₇ group is connected to five different cations, i.e. four Eu1 and one Eu2. The disilicate group consists of two SiO₄ tetrahedra sharing an O atom, denoted O3, with a bridging bond angle Si–O–Si of 136.7(6)°. Observed individual Si–O distances are in the acceptable range for silicate structures. The bridging Si–O bond [1.661 (4) Å] is expectedly longer than the nonbridging Si–O bonds [1.616 (5) and 1.622 (7) Å]. The O–Si–O bond angles range from 106.7 (2) to 111.0 (4)°.

Three potassium cations show three different coordination environments. The coordination sphere of K1 includes eight oxygen ions and forms a K1O₂₊₄₊₂ coordination polyhedron which can be described as a distorted hexagonal pyramid with a split apex [distances range from 2.770 (5) to 3.049 (5) Å]. K2 atom is coordinated by nine oxygen atoms with distances from 2.923 (4) to 3.029 (3) Å providing a regular tricapped trigonal prism (K2O₆₊₃). The coordination of the K3 atom (CN=6) can be described as undistorted trigonal antiprism [K–O = 2.754 (7) Å].

Bond-valence calculations show that the bond valences are well balanced and the K–O, Eu–O and Si–O bond lengths are consistent with the presence of K⁺, Eu³⁺, Si⁴⁺ and O²⁻ in structure. Only the bond-valence sum for Eu1 is oversaturated (3.42 v.u.) which can be attributed to the environment of the Eu1O₆ octahedron. All oxygen atoms from Eu1O₆ octahedron are common to all adjacent polyhedra around the K1 and K2 atoms for which BVS shows slightly undersaturated values. This means that slightly deviating bonds are formed in order to satisfy the local valence disagreement due to structural disorder. These values are in accordance with the literature data for K₃REESi₂O₇¹³ that contains the rare-earth cation in both slightly distorted octahedral and an ideal trigonal prismatic coordination environment. The results of bond-valence-sum calculations (Valist software;²³ bond valence parameters: Brown & Altermatt²⁴ and Brese & O’Keeffe²⁵), are presented in Table III.

TABLE III. Bond valence sums for the cations and anions in $K_3EuSi_2O_7$. References for bond valence parameters are given in footnotes.

	Bond valence, v. u.						Σv_{ij} / v. u.
	K1 ^a	K2 ^a	K3 ^a	Eu1 ^a	Eu2 ^a	Si ^b	
O1	0.178×2 0.094×2 0.084×2	0.118×6		0.57×6		1.022×2	2.066
O2	0.106×2		0.186×6		0.495×6	1.005	1.898
O3		0.089×3				0.905	1.988
Σv_{ij} / v. u.	0.924	0.975	1.116	3.42	2.97	3.954	

^aBrown & Altermatt²⁴; ^bBrese & O'Keeffe²⁵

X-ray powder diffraction (XRPD)

Collected XRPD data are shown in Fig. 4. A diffraction pattern calculated using the CIF file obtained from the single-crystal data of $K_3EuSi_2O_7$ was overlaid. The experimental XRPD patterns are in good agreement with those calculated from the CIF.

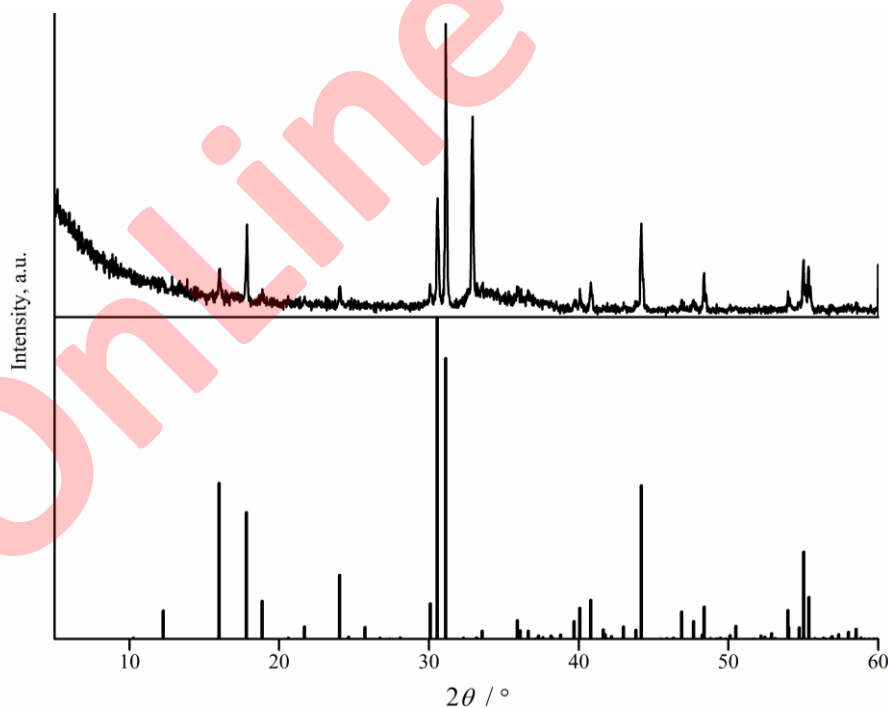


Fig. 4. X-ray powder diffraction pattern of $K_3EuSi_2O_7$. Upper pattern represents experimental data while lower pattern represents overlaid positions of Bragg's peaks calculated from $K_3EuSi_2O_7$ CIF.

Scanning electron microscopy (SEM)

The crystal morphology of a single $\text{K}_3\text{EuSi}_2\text{O}_7$ crystal obtained using a SEM is shown in Fig. 5. Elongated prismatic crystal is clearly visible. Crystal looks homogeneous. Similar crystal morphology was reported also by Bondar and co-authors,¹¹ although their crystals are much thicker and less elongated.

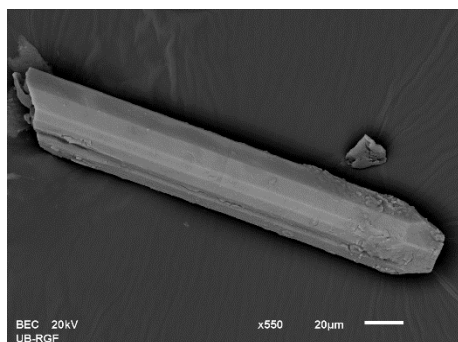


Fig. 5. Scanning electron microscope (SEM) micrograph of the $\text{K}_3\text{EuSi}_2\text{O}_7$ crystal.

CONCLUSION

Single crystals of $\text{K}_3\text{EuSi}_2\text{O}_7$ were prepared by high-temperature flux crystal growth and were characterized by single-crystal X-ray diffraction, powder X-ray diffraction and SEM analysis. The compound crystallizes like disilicates containing the larger REEs, i.e. Nd, Sm, Eu, Gd, Tb, Dy, Ho, Er, Tm, Yb and Y, with the exception of Er and Y, which can crystallize as polymorphs in space groups $P6_3/mcm$ and $P6_3/mmc$. Their effective ionic radii range from 0.983 Å for VI Nd^{3+} to 0.868 Å for VI Yb^{3+} ($\text{VI Eu}^{3+} = 0.947$ Å).²⁶ The structure of these compounds contains the rare-earth cation in both a slightly distorted octahedral and an ideal trigonal prismatic coordination environment.

SUPPLEMENTARY MATERIAL

The crystallographic data for this paper have been deposited with the Cambridge Crystallographic Data Centre under deposition number CCDC 2062974.

Acknowledgements: The authors gratefully acknowledge financial support from the Ministry of Education, Science and Technological Development of the Republic of Serbia (Grant No. III45007 and III45015); Ministry of Education, Science and Technological Development of the Republic of Serbia & Austria Federal Ministry of Education, Science and Research (project No. 451-03-02141/2017-09/14; WTZ project No. SRB 14/2018). The authors also thank the Laboratory for Scanning Electron Microscopy at the Department of Mineralogy, Crystallography, Petrology and Geochemistry, University of Belgrade, Faculty of Mining and Geology and the Laboratory of X-ray diffraction at the Department of Physics, University of Novi Sad, Faculty of Sciences.

ИЗВОД
КРИСТАЛНА СТРУКТУРА $K_3EuSi_2O_7$

САБИНА З. КОВАЧ, ПРЕДРАГ З. ДАБИЋ И АЛЕКСАНДАР С. КРЕМЕНИВИЋ

Универзитет у Београду, Рударско – геолошки факултет, Департаман за минералогију,
кристалографију, петрологију и геохемију, Лабораторија за кристалографију, Бушина 7,
11000 Београд, Србија

У оквиру испитивања алкалних силиката елемената ретких земаља добијених методом флукса из растопа, синтетисан је трикалијум еуропијум дисиликат, $K_3EuSi_2O_7$. Кристална структура одређена је методом рендгенске дифракције на монокристалу. Кристалише у просторној групи $P6_3/mcm$. У кристалној структури испитиваног једињења, део Еу катјона је у благо деформисаној октаедарској координацији, а други део је у идеалном тригонално-призматичном координационом окружењу. Дисиликатне групе Si_2O_7 повезују четири EuO_6 октаедра и једну EuO_6 тригоналну призму. Између њих се налазе три различито координисана катјона калијума. Силикати који садрже веће јоне ретких земаља имају структуру која садржи катјон ретке земље у два различита координациона окружења: у благо искривљеном октаедру и у идеалном тригонално-призматичном окружењу.

(Примљено 18. фебруара; ревидирано 15. марта; прихваћено 31. марта 2021.)

REFERENCES

1. J. Felsche, *In The Crystal Chemistry of the Rare-Earth Silicates. Rare Earths. Structure and Bonding*, Vol. 13, Heidelberg: Springer, Berlin, Germany, 1973 (https://doi.org/10.1007/3-540-06125-8_3)
2. A. Kitai, *In Luminescent Materials and Applications*, John Wiley & Sons Ltd., Chichester, England, 2008 (Online ISBN:9780470985687)
3. A. M. Latshaw, W. M. Chance, N. Trenor, G. Morrison, M. D. Smith, J. Yeon, D. E. Williams, H.-C. zur Loye, *CrystEngComm* **17** (2015) 4691 (<https://doi.org/10.1039/C5CE00630A>)
4. A. M. Latshaw, K. D. Hughey, M. D. Smith, J. Yeon, H.-C. zur Loye, *Inorg. Chem.* **54** (2015) 876 (<https://doi.org/10.1021/ic502185b>)
5. A. M. Latshaw, B. O. Wilkins, K. D. Hughey, J. Yeon, D. E. Williams, T. T. Tran, P. S. Halasyamani, H.-C. zur Loye, *CrystEngComm* **17** (2015) 4654 (<https://doi.org/10.1039/C5CE00671F>)
6. A. M. Latshaw, G. Morrison, K. D. zur Loye, A. R. Myers, M. D. Smith, H.-C. zur Loye, *CrystEngComm* **18** (2016) 2294 (<https://doi.org/10.1039/C6CE00177G>)
7. A. M. Latshaw, J. Yeon, M. D. Smith, H.-C. zur Loye, *J. Solid State Chem.* **235** (2016) 100 (<https://doi.org/10.1016/j.jssc.2015.12.013>)
8. G. Morrison, A. M. Latshaw, N. R. Spagnuolo, H.-C. Zur Loye, *J. Am. Chem. Soc.* **139** (2017) 14743 (<https://doi.org/10.1021/jacs.7b08559>)
9. B. R. Figueiredo, A. A. Valente, Z. Lin, C. M. Silva, *Micropor. Mesopor. Mat.* **234** (2016) 73 (<https://doi.org/10.1016/j.micromeso.2016.07.004>)
10. F. Liebau, *Structural chemistry of silicates: structure, bonding and classification*, Heidelberg: Springer, Berlin, Germany, 1985, p. 347 (<https://doi.org/10.1007/978-3-642-50076-3>)
11. I. A. Bondar, T. F. Tennisheva, Y. F. Shepelev, N. A. Toropov, *Dokl. Akad. Nauk SSSR* **160** (1965) 1069 (<http://www.mathnet.ru/links/df924f2db1305a2430f200e3f58341c7/dan30741.pdf>)

12. M. S. Hwang, H. Y.-P. Hong, M. C. Cheng, Y. Wang, *Acta Cryst.* **C43** (1987) 1241 (<https://doi.org/10.1107/S0108270187092308>)
13. I. Vidican, M. Smith, M., H.-C. zur Loye, *J. Solid State Chem.* **170** (2003) 203 ([https://doi.org/10.1016/S0022-4596\(02\)00029-4](https://doi.org/10.1016/S0022-4596(02)00029-4))
14. J. D. Napper, R. C. Layland, M. D. Smith, H. Loye, *J. Chem. Crystallogr.* **34** (2004) 347 (<https://doi.org/10.1023/B:JOCC.0000028666.53348.fc>)
15. P. Dabić, M. G. Nikolić, S. Kovač, A. Kremenović, *Acta Cryst.* **C75** (2019) 1417 (<https://doi.org/10.1107/S2053229619011926>)
16. A. Myers, *Journal of the South Carolina Academy of Science* **12** (2014) 200 (<https://scholarcommons.sc.edu/jscas/vol12/iss1/1>)
17. Rigaku Oxford Diffraction, CrysAlis^{Pro} Software system, Rigaku Corporation, Oxford, 2018
18. Rigaku. PDXL 2: Integrated powder X-ray diffraction software. Version 2.8.3.0. Rigaku Corporation, Tokyo, Japan, 2007 (<https://www.rigaku.com/en/service/software/pdxi>)
19. R. C. Clark, J. S. Reid, *Acta Cryst.* **A51** (1995) 887 (<https://doi.org/10.1107/S0108767395007367>)
20. G. M. Sheldrick, *Acta Cryst.* **C71** (2015) 3 (<https://doi.org/10.1107/S2053229614024218>)
21. M. Momma, F. Izumi, *J. Appl. Cryst.* **44** (2011) 1272 (<https://doi.org/10.1107/S0021889811038970>)
22. P. Dabić, V. Kahlenberg, B. Krueger, M. Rodić, S. Kovač, J. Blanuša, Z. Jagličić, Lj. Karanović, V. Petriček, A. Kremenović, *Acta Crystallogr. B* in review
23. A. S. Wills, *Valist*, 2010. Program available from www.CCP14.ac.uk
24. I. D. Brown, D. Altermatt, *Acta Cryst.* **B41** (1985) 244 (<https://doi.org/10.1107/S0108768185002063>)
25. N. E. Brese, M. O'Keeffe, *Acta Cryst.* **B47** (1991) 192 (<https://doi.org/10.1107/S0108768190011041>)
26. R. D. Shannon, *Acta Cryst.* **A32** (1976) 751 (<https://doi.org/10.1107/S0567739476001551>)